

CHARACTERISTIC STUDY ON BEHAVIOUR OF INTEGRAL CRYSTALLINE WATER PROOFING CONCRETE

R Vijayalakshmi¹, D. Dinesh Babu², M. Mathivanan³, J. Sandeepkumar⁴,

V. Boopathiraja⁵

1.Assit. Professor, 2,3,4,5. UG Student, Civil Dept., Nadar Saraswathi College of Engineering and Technology, Theni, Tamil Nadu, India.

Abstract - Integral Crystalline Waterproofing blocks the movement of water through the concrete by plugging or blocking the natural pores, capillaries and micro cracks, and concrete its own waterproofing barrier. This stands in contrast to more conventional means of waterproofing, which usually involves applying a coating or coated to the concrete surface. The process is sometimes also attempted through densification of the concrete Crystalline waterproofing systems rely on a technology that turns porous concrete in to an impermeable barrier. The result of these technology the structure with reduced cracking, self-sealing and waterproofing abilities which provides a powerful defense against water and resist corrosion of reinforcing steel. In this paper the water crystalline formation is arrested by the partial replacements of cement by GGBS, Silica Fume, Fly Ash and Rice Husk ash with addition of CWP agent. This characteristic strength is analyzed by compressive, split tensile and flexural strength of conventional concrete compared by replacement concrete.

Key words: Crystalline Waterproofing Agent CWA, Ground Granulated Blast Furnace Slag GGBS, Silica Fume SF, Fly

Ash FA, Rice Husk Ash RA

1. INTRODUCTION

1.1 Waterproofing

Concrete is currently the most used human made material in the world, used twice as much as all other materials combined. The concrete degradation is the root cause of the issue in the presence of moisture or water within the concrete. The ingress of deleterious substances into concrete takes place through the pore system in the concrete matrix, or through micro cracks.

To ensure a concrete structure's durability, which leads to a longer lifespan and a more sustainable building, the concrete must be waterproofed.

1.2 Integral Crystalline Water Proofing

Integral Crystalline Waterproofing (ICW) technology is based on principles that are very similar to the processes that occur during concrete hydration. These admixtures are added or applied to concrete, crystalline chemicals facilitate a reaction with cement to form long, narrow crystals and

filling the pores, capillaries and hairline cracks of the concrete mass. The moisture content remains present, till the crystals continue to grow throughout the concrete. Once the concrete has dried, the crystalline chemicals sit dormant until another dose of water (such as through a new crack) causes the chemical reaction known as crystallization to begin again. The ability to reactivate in the presence of water gives crystalline-treated concrete the ability to improve self-sealing. When cracks form due to drying shrinkage, settling, seismic activity, etc., water entering through them causes new crystals to form and grow, blocking and filling the cracks. Improving the self-sealing ability of concrete is one of crystalline technology's most unique and useful features, and can help to dramatically reduce the long-term maintenance and repair costs of a concrete structure.



Fig 1 crystalline water proofing agent

1.3 Partial Replacement of Cement in Concrete

Concrete is a family of different material like binding material (cement+ fly ash), fine aggregate, coarse aggregate and water. Nowadays, cost of construction is very high with usage of conventional materials due to unavailability of natural materials. To overcome this, by total replacement of concrete with different material which is not convenient in terms of required properties. The limitation of unavailability of material which plays the vital role of concrete. So we have only choice of partial replacement of concrete ingredients by waste materials. The partial replacement of cement with desirable properties that we can save natural material and reduce emission of CO₂ in the atmosphere. The industrial wastes dumping to the nearest site which spoils the land and atmosphere. It also affects the aesthetics of urban environment and so the use of this waste material in concrete is cost effective as well as environment friendly.

2. MATERIAL USED

2.1 Fly Ash

Fly Ash is a fine powder obtained from thermal power plant. It is a coal combustion product and it is also known as Pulverized Fuel Ash as a by-product. The shape of the particles is spherical and the size ranges from 0.5 μm to 300 μm . Fly ash consists of substantial amount of SiO_2 , Al_2O_3 , CaO . Fly ash as a partial replacement of cement up to 30 % of mass of the cement. It improves the workability of concrete and reduce the emission of CO_2 in concrete.

2.2 Ground Granulated Blast Furnace Slag (GGBS)

Ground-Granulated Blast-Furnace Slag (GGBS) is a cementitious material and it is a by-product of furnaces making iron. It contains a maximum amount of calcium oxide and silica. The physical appearance of GGBS is fine powder and colour is of off - white. GGBS as a partial replacement of cement up to 30-50 %. It increases the durability of concrete. It sets very slowly. It produces the low heat of hydration.

2.3 Silica Fume

Silica fume is an ultra-fine powder collected from by-product of making silicon and ferrosilicon. It consists of spherical particles and the average diameter of particle is 150 μm . It consists of 85 – 95 % of Silicon di-oxide. It increases the compressive strength, bond strength and abrasion resistance.

2.4 Rice Husk Ash

The optimized RHA, by controlled burn and/or grinding, has been used as a pozzolanic material in cement and concrete. It improves the strength and durability properties, and environmental benefits to disposal of waste materials and to reduced carbon dioxide emissions. The optimum level of RHA added to the cement up to 25% to increase the strength and durability.

2.5 Super Plasticizer (Poly Carboxylate)

Superplasticizers is a chemical admixture and it also high range water reducer. It used in low dosage up to 0.15 % to 3% and they allow to reduce the water up to 40%.it increase the fluidity properties of concrete in low w/c ratio. It improves the compressive strength and flexural strength of concrete.

3. Tests

Compressive strength of concrete is depending on the water-cement ratio, grade of cement, quality of aggregates, and quality control during production of concrete. We carried out the compressive test on cube by various standard codes recommend concrete concrete cube as the standard specimen for the test.

3.1 PARTIALLY REPLACEMENT OF FLY ASH IN CEMENT WITH CRYSTALLINE WATER PROOFING AGENT

Grade of Concrete – M30

Type of Cement – OPC 53

Crystalline Water Proofing Agent – 2 %

Fly Ash – 10 %

Superplasticizer – 1 %

W/C Ratio – 0.4

Consistency of OPC with Fly Ash - 45 %

Initial setting time – 110 mins

Slump value – 21 mm


Compaction factor - 0.875

Flow table value – 7.2 %

Vee Bee time - 12 sec

Days	1	2	3	Average
7 days N/mm ²	29.33	23.55	23.11	25.33
14days N/mm ²	33.725	27.08	27.68	29.49
28days N/mm ²	40.44	37.78	38.65	38.96

Table 1: Fly Ash with CWA

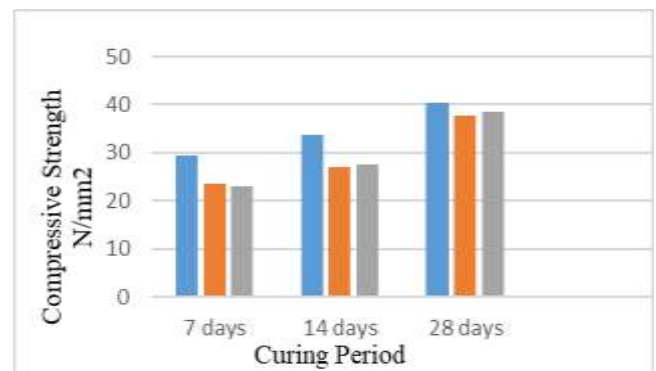

Graph 1: Fly Ash with CWA

3.2 PARTIALLY REPLACEMENT OF SILICA FUME IN CEMENT WITH CRYSTALLINE WATER PROOFING AGENT

Grade of concrete – M30

Type of cement – OPC 53

Crystalline water proofing agent – 2 %

Silica fume – 10 %

Superplasticizer – 1 %

w/c ratio – 0.4

Consistency of OPC with silica fume – 35 %

Initial setting time – 95 mins

Slump value – 113 mm


Compaction factor - 0.755

Flow table value – 10.2 %

Vee Bee time - 7 sec

Days	1	2	3	Average
7 days N/mm²	40.44	39.55	40	40
14days N/mm²	42.50	43.48	43	43
28days N/mm²	44.44	46.67	46.36	45.82

Table 2: Silica Fume with CWA

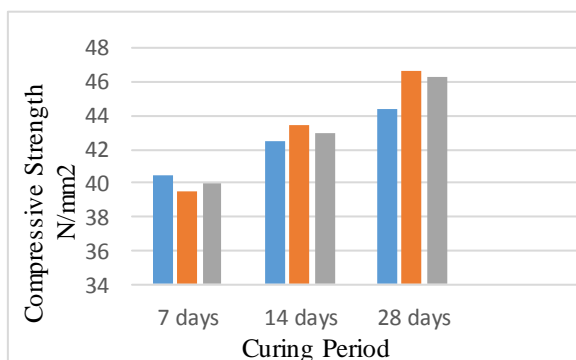

3.3 PARTIALLY REPLACEMENT OF GGBS IN CEMENT WITH CRYSTALLINE WATER PROOFING AGENT

Grade of concrete – M30

Type of cement – OPC 53

Crystalline water proofing agent – 2 %

GGBS – 20 %

Superplasticizer – 1 %

w/c ratio – 0.4

Consistency of OPC with GGBS – 35 %

Initial setting time – 120 mins

Slump value – 96 mm


Compaction factor - 0.715

Flow table value – 11.6 %

Vee Bee time - 6 sec

Days	1	2	3	Average
7 days N/mm²	33.33	42.67	31.11	35.70
14 days N/mm²	38.33	49.07	35.77	41.06
28 days N/mm²	43.33	55.47	40.44	46.41

Table 3: GGBS with CWA

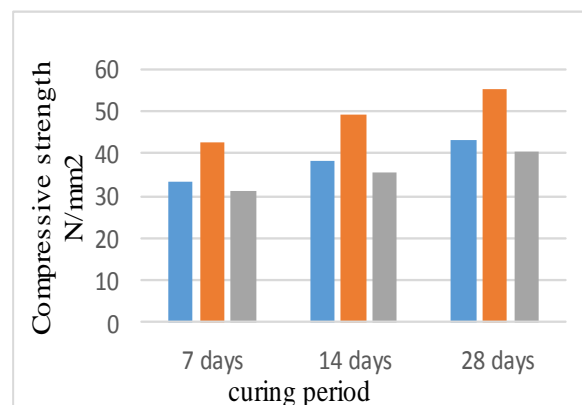

Graph 3: GGBS with CWA

3.4 PARTIALLY REPLACEMENT OF RICE HUSK ASH IN CEMENT WITH CRYSTALLINE WATER PROOFING AGENT

Grade of concrete – M30

Type of cement – OPC 53

Crystalline water proofing agent – 2 %

Rice Husk Ash – 25 %

Superplasticizer – 1 %

w/c ratio – 0.4

Consistency of OPC with RHA – 55 %

Initial setting time – 195 mins

Slump value – 40 mm


Compaction factor - 0.715

Flow table value – 6.6 %

Vee Bee time - 19 sec

Days	1	2	3	Average
7 days N/mm ²	20	18.22	20	19.4
14 days N/mm ²	26.3	28.95	27.94	27.73
28 days N/mm ²	32	40	34.2	35.4

Table 4: RHA with CWA

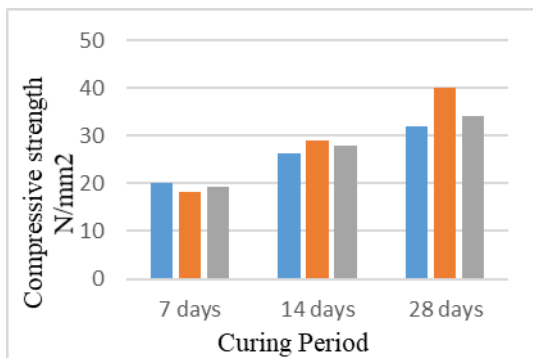

Graph 4: RHA with CWA

4. COMPARATIVE STUDY

Four admixtures were taken out (i.e.) Fly ash, GGBS, Silica fume, Rice husk ash and it will be added as a partial replacement in cement. It also includes the addition of Crystalline Waterproofing agent. It will be added to each of the replacement. The replacement is determined by referring journals and fixed its percentage. (i.e.),

Fly Ash – 10%

GGBS – 20%

Silica fume – 10%

Rice Husk Ash – 25%

Crystalline Waterproofing agent – 2% Each replacement, 3 Cubes were casted and tested on 7, 14, 28 days respectively. The addition of crystalline waterproofing agent determines whether the concrete is attaining to reduce its moisture content (i.e.) (filling the voids by growing crystals in it). It also acts as a self-sealing agent. compressive strength of Fly ash, GGBS,

Silica Fume, Rice Husk Ash is computed on following graph.



Graph 5: Comparative Study

5. CONCLUSION

Fly ash, GGBS, Silica fume, Rice husk ash can be added as a partial replacement of. The use of Fly ash with addition of crystalline waterproofing agent gives low strength at 28-days. GGBS replaces partially, it gives very good results and a greener approach in construction and sustainable development. In addition of crystalline waterproofing agent, it gives better strength. Cement replacement up to 10% with silica fume leads to increase in compressive strength, for M30 grade of concrete. The use of rice husk ash with addition of crystalline waterproofing agent gives poor strength at 28-days.

6. REFERENCES

- 1 Alefiya Kachwala, Arti Pamnani, Amit Raval “ Effect of Rice Husk Ash as a Partial Replacement of Ordinary Portland cement in Concrete”
- 2 C. Edvardsen, “Water Penetrability and Autogenous Healing of Separation Cracks In Concrete” BetonwerkundFertigteil-Technik, vol.62, no.11, pp.77–85,1996.
- 3 Guo-Zhong LU1, et al., “The Analysis On Mechanism and Application of Cementitious Capillary Crystalline Waterproofing Coating”
- 4 Johann Plank, Christof Schroefl, Mirko Gruber, Matthias Lesti, Roland Sieber “Effectiveness of Polycarboxylate Superplasticizers in Ultra-High Strength Concrete: The Importance of PCE Compatibility with Silica Fume”

- 5 B. Kaviya.R, et al., Bharath University, Chennai. "Study On Partial Replacement of Cement by Ground Granulated Blast Furnace Slag (Ggbs)"
- 6 Navrit Bhandari¹, Col. Harry Sidhu², Dr. Sanjay K Sharma³ "To Determine the Efficacy of Crystalline Waterproofing System in Concrete"
- 7 Ram Kumar¹, et al., Department of Civil Engineering Om Institute of Technology & Management, (Hisar), Haryana "Partial Replacement Of Cement With Silica Fume And Its Effects On Concrete Properties"
- 8 Er. Ravi Bhushan, et al., " Partial Replacement of Cement by Rice Husk Ash"
- 9 Richard P. Kadlubowski, AIA and Dean W. Yates, AIA "Waterproofing Challenges In Concerete"
- 10 T.G.S Kiran, M.K.M.V Ratnam "Fly Ash as a Partial Replacement of Cement in Concrete and Durability Study"
- 11 V.Rahhal, et al., "Scheme of The Portland Cement Hydration With Crystalline Mineral Admixtures And Other Aspects." *Silicates Industriels*, vol. 74, no.11-12, pp.347-352,2009.
- 12 Vinod Goud, et al., "Partial Replacement Of Cement With Fly Ash In Concrete And Its Effect"
- 13 xypex chemical corporation "Crystalline Water Proofing Technology; Improving Durability "
- 14 Yogendra O. Patil, Prof. P.N. Patil, Dr. Arun Kumar Dwivedi "GGBS as Partial Replacement of OPC in Cement Concrete – An Experimental Study"