

Experimental Study on Load Carrying Capacity of RCC Beam by Using GFRP Pultruded Profiles

Chetan Sanjay Kautkar¹, Prof. Vishwajeet Kadlag², Dr. Ashok kansnale³

¹ M.E. Student, Department of civil engineering Dr. D. Y. Patil School of Engineering, Pune- 412 105, India.

² Professor, Department of civil engineering, Dr. D. Y. Patil School of Engineering, Pune-412 105, India.

³ Principal, Dr. D. Y. Patil School of Engineering, Pune-412 105, India.

Abstract - Steel widely used as reinforcement material in construction industry. But, steel fails to perform structurally when it exposed to harsh environment such as bridges, chemical plants and other structures. This has been already tested on GFRP bars many techniques to prevent corrosion of steel reinforcement. When steel bars are replaced by GFRP bars to reinforce composite beams, brittle failure of GFRP bars caused due lack of ductility of beam members. Due to lack of ductility of conventional beam both stiffness and ultimate load were reduced significantly. Therefore for overcoming these effects we introduced GFRP I-section beam and C-Channel section in conventional beam. Pultruded GFRP I-section beam and C-Channel section are usually made by pultrusion process. In pultrusion process, materials such as fiberglass & resin are pulling by extrusion process. In this experimental study on load carrying capacity, failure pattern and deflection of a composite beam, which is reinforced with longitudinal tensile steel bars as well as glass fibre reinforced polymer (GFRP) pultruded I-section beam and C-Channel section encased in concrete. Six beam specimens, including one Conventional reinforced concrete (RC) beam, GFRP I-beam in center and GFRP I-beam bottom, GFRP C-channel in center and GFRP C-channel bottom and GFRP I-beam is replaced by bottom steel bars, were cast and tested under two-point bending. Result will use to analyze Load carrying capacity of beam. The present project work aims for studying suitability of GFRP as strengthened material for rolled RC beam. So in this paper to study load carrying capacity of RC beam strengthened with glass fiber reinforced polymer I-section beam and C-channel section. Also, check suitable position and pattern of pultruded GFRP member.

Key Words: GFRP I-section Beam and C-section Channel, RCC composite beams, Load carrying capacity.

1. INTRODUCTION

In previous works done on repair and strengthening of steel and RCC structures by use of FRP materials. An FRP structure generally consist raw materials such as glass

roving, glass mat & surface veil, unstructured polyester (UP), Resin applied to mould in combination with steel reinforcement, most commonly glass fiber, to form a part which is rigid, highly durable & lightweight.

Due to low maintenance & lightweight, FRP is used in many applications building & infrastructure projects. To cast synthetic marble & solid surface for kitchens, bathrooms and roof tiles, UP resins can be mixed with glass fiber & fillers. FRP is more suitable option to conventional materials for huge projects like bridges, wind generators because it has advantages like lightweight, low maintenance & easy installation process.

Fiber Reinforced Polymer (FRP) is increasingly used in civil engineering construction in last two decades because of excellent properties of corrosion resistance as well as high strength & lightweight. Wide research has been conducted on to retrofit existing structures by using FRP

Whereas, FRP composites such as FRP bars and FRP pultruded profiles are also exploited as standard construction product for new construction. Due to advantages of convenient installation and customized cross-sections (e.g. I-beam, square tube or circular tube), application of FRP pultruded profiles it has been widely used in recent year). FRP pultruded profiles are suitable for use as all FRP structures such as building floor, cooling towers and offshore platforms. Moreover, it can be used in combination with other materials to develop composite structures. Lot of research were carried out on GFRP I-beam reinforced beam specimen, thus forming a composite structural member.

In order to improve the load carrying capacity of the composite beam reinforced with I-beam and C-channel, a type of composite beam is proposed in this study. The composite beam created by using I beam & longitudinal tensile steel bars, and those I beam is encased in concrete. The load carrying capacity and corrosion resistance of conventional beam members are increased by encased of GFRP I-beam or C-channel is contributed to improvement of to achieve enough bending, stiffness and ductility of composite beams use tensile steel bars in this composite beam. The concept of incorporating FRP and steel materials together to enhance ductility of structure has been proven to be effective by both experimental and numerical approaches. Steel stirrups are employed to

confine the concrete and enhance the shear strength of beam members.

The advantages of this type of composite beams are apparent when compared with existing conventional beams. Compared with the conventional beam reinforced with composite beam with GFRP I-section, although configurations of both are similar, self-weight of the Proposed composite beam is decreased & the corrosion resistance capacity is increased due to existence of I-beam. In comparison of composite beam with GFRP I-beam, there are below advantages of composite beam:

- Due to surroundings concrete of I -beam fire performance can be improved
- Stability of the I-beam can be increased due to encased in concrete; and
- By using tensile steel bar ductility can be improved.
- In type of composite beam also have significant advantages in practical applications, such as:
- All materials which are using that is standard which is without special treatment like drilling holes, riveting or welding

Because of existence if steel bars inside, it is easy for connecting columns.

2. METHODOLOGY

Pultrusion: Pultruded FRP sections are usually made by pultrusion process. By pulling raw material composite through a heated die, this process creates continuous composite profile. In pultrusion process extrusion is pulling of materials such as fibreglass and resin, through a shaping die.

Polyester, polyurethane and vinyl ester epoxy resins etc. are types of resin can be used in pultrusion including Fiber is wetted or impregnated with resin and is organized and then removed of excess resin. After that composite is passed through a heated steel die. Puller clamps also provided for pulling structural profile.

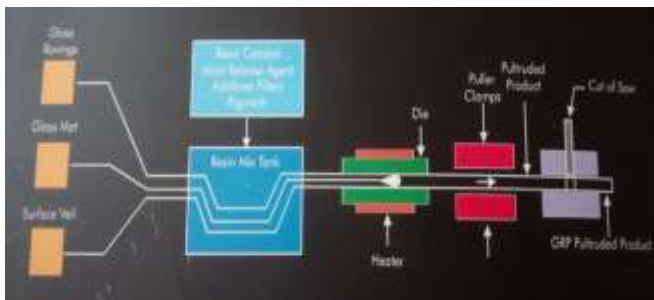


Fig -1: Pultrusion Process

Mechanical, physical and electrical properties of GFRP I-section beam and C-channel gives by manufacturer **Atul Electro Formers Ltd., Pune.**

Table -1: Mechanical, physical and electrical properties of GFRP I-section beam and C-channel section.

Description	Code No	Minimum Required	Material value
Density	ASTM D 792	-	1.9
Barcol Hardness	ASTM D 2583,	50-65	50
Water Absorption	ASTM D 570,	< 0.25%	0.24%
Ultimate Tensile Strength	ASTM D 638,	392 Mpa	403 Mpa
Flexural Strength	ASTM D 790,	245 Mpa	400 mpa
Compressive Strength	ASTM D 638,	150	150 mpa
Flammability	UL 94 V0	-	-
Flammability	[IS : 6746, CLASS 1] / PR	-	-
Sp. Gravity	IS : 10192	-	-
Fire Retardancy	IS : 11731, PASS	-	-
Surface Burning	ASTM E-84 / IS : 6746,	< 15	8
Dielectric Strength (Axial)	ASTM D 149,	1.2 KV/MM	4.8 KV/MM
Dielectric Strength (Radial)	ASTM D 149,	10.0 KV/MM	33.7 KV/MM
Arc Resistance	ASTM D 495	120s	122.7s
Oxygen Index	ASTM D 2863,	30	41
UV Resistance	RESIN MFR. TC	-	-

Collection of required material like cement, sand, aggregate, GFRP I-section, GFRP C-channel section, steel etc. is done. The cross section of an elements comprises of beam size is 150 X 150 X 700 mm with 2#8 mm diameter steel bars at top & 2#8 mm diameter steel bars bottom and 6 mm stirrups at spacing 100mm c/c inclusive of GFRP I and C Channel section.

Evaluate load carrying capacity of reinforced elements of M20 grade and determine corresponding strength after 28 days by applying two point loading. Comparisons of results with conventional beam, composite beam using GFRP I-beam and composite beam using GFRP C-channel.

3. MODELLING

The reinforcement of beam 2#8mm diameter use for main bar, 2#8 mm Anchor bar and 6 mm@100mm c/c diameter use for stirrups.40mm×25mm×3mm (web × flange × thickness) of GFRP I-section placed at bottom, center, and replacement of main bar for load carrying

capacity of RCC beam. 40mm×25mm×3mm (web × flange × thickness) of GFRP C-channel placed at bottom and center for taking load carrying capacity of RCC beam.

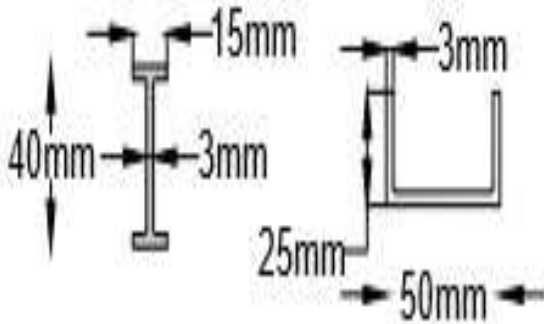


Fig -2: Details I-section beam and C-channel of GFRP

3.1 Detailing of Specimen

For this investigation Specimen specification was consider as per following specification for RCC beam by using I-section beam and C-channel of GFRP. Total 18 number specimens will be casted then testing of beams on Universal Testing Machine (UTM) by applying two point loads on a beam.

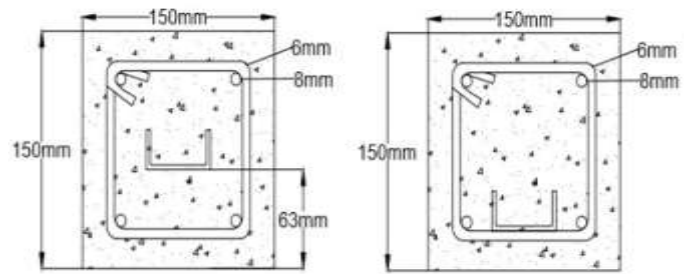
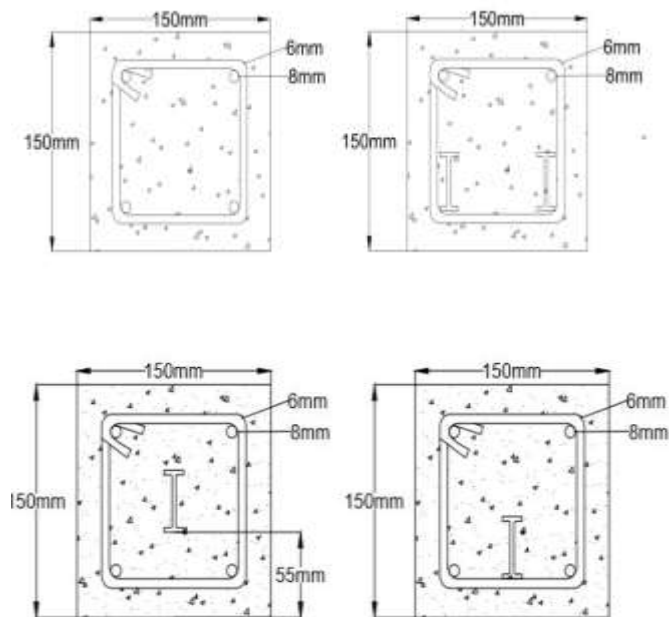


Fig -3: Different combination of beams

The beam dimensions selected: 700 mm X 150mm X 150mm (length x width x depth)

GFRP I- beam dimensions: 40 X 15 X 3 mm (web × flange × thickness)

GFRP C-channel dimensions: 50mm X 25 X 3 mm (web × flange × thickness)

Table -2: Percentage of material in beams

Sr. No.	Name of Specimen	% of area of bottom steel	% of area of GFRP
1.	Conventional beam	0.44%	0%
2.	I section beam in bottom or center position	0.44%	0.58%
3.	C channel section in bottom or center position	0.44%	0.92%
4.	Double I section beam in bottom	0%	1.17%

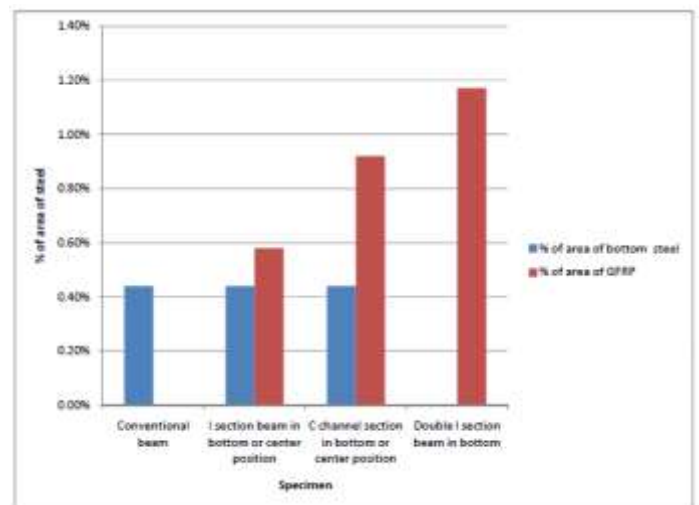


Chart-1: Chart of % Percentage of material in beams



Fig -4: Casting of I-section GFRP beam



Fig -5: Casting of C-Channel GFRP beam

3.2 Test Setup

The eighteen specimens were tested with Centre point bending with 700mm effective span. The sample was placed on two supporting pins a set distance apart. Load specimen continuously without shock. The load applied at constant rate to the breaking point. The load applied at the rate of 0.9- 1.2 MPa/min. The specimens' cracks will map and the observations were record during the loading and at the time of failure.

4. Result and Discussion

4.1 Load Carrying Capacity

Table -3: Load Carrying Capacity of Samples by Experimentally

Specimen	Load Carying Capacity	Average Load Carying capacity
1IC	69	69.80
2IC	68	
3IC	72.4	
12IB	72	72.33
22IB	70	
32IB	75	
1IB	71	72.00
2IB	76	

3IB	69	63.93
1CC	58.6	
2CC	65	
3CC	68.2	67.17
1CB	65.2	
2CB	66.3	
3CB	70	55.00
1A	55	
2A	52	
3A	58	

Numbers:-Specimen No.

IC:- I-Section GFRP Beam In Center Position

2IB:- Double I-section GFRP Beam in bottom position as main steel

IB:- I Section GFRP Beam in Bottom position

CC:- Channel Section GFRP in center position

CB:-Channel Section GFRP in bottom position

A:- Conventional Beam

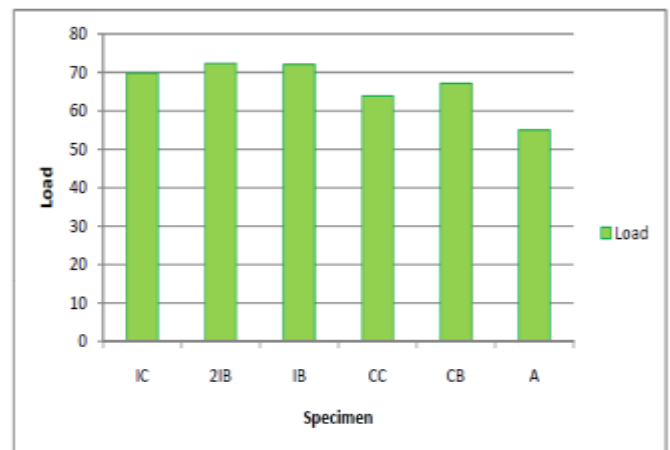


Chart-2: Load Carrying Capacity of Beams

Load carrying capacity of various beams by experimentally carried out. Percentage of increased load carrying capacity of conventional beam is compared with GFRP RC beam.

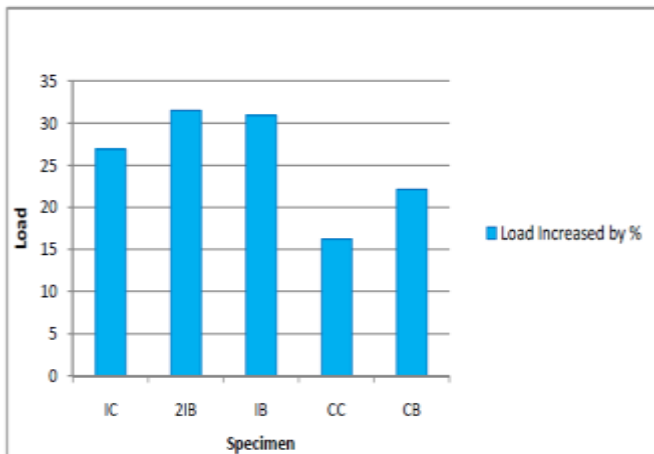


Chart-3: Percentage of increased load carrying capacity of Beams

Load carrying capacity of various beams having different section of GFRP, position is carried out. It is observed that load carrying capacity of 2IB is increased i.e., 31.51% than conventional beam. IB is combination of steel and GFRP I-beam having load carrying capacity increased by 30.90% than conventional beam.

4.2 Results of Load Carrying Capacity Vs Deflection

Table -4: Load Vs Deflection

Load	Deflection (mm)					
	IC	2IB	IB	CC	CB	A
0	0.0	0	0	0	0	0
5	0.7	0.6	0.1	0.1	0.2	0.8
10	1.2	1	0.3	0.3	0.4	1.1
15	1.4	1.4	0	0.5	0.6	1.5
20	1.7	1.6	0.5	0.8	0.9	1.8
25	2.1	1.9	0.5	1	1.3	2
30	2.5	2.1	0.9	1.4	1.7	2.4
35	2.8	2.3	1.1	1.6	2.1	2.8
40	3.1	2.6	1.3	1.9	2.4	3.2
45	3.4	2.9	1.7	2.2	2.9	3.6
50	3.8	3.3	2.1	2.8	3.3	4.1
55	4.2	3.5	2.5	3.5	3.8	5.1
60	4.6	3.9	3	4.3	4.4	5.4
65	5.1	4.3	3.7	4.5	5.3	
70	5.7	5	4.6	4.7	6.7	
75		5.2	4.9			

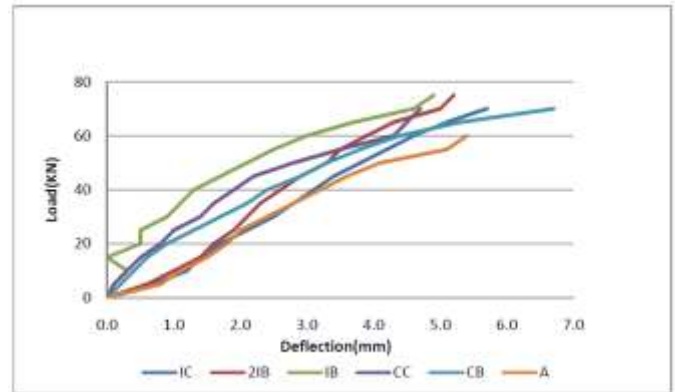


Chart-4: Load carrying capacity Vs Deflection curves

Load carrying capacity Vs Deflection curves of experimental results are plotted. It is observed that load carrying capacity increases deflection also increases that is load carrying capacity is directly proportion to deflection. Load carrying capacity is more GFRP I-section beam in case in RC beam compare to other cases & Deflection is less in GFRP C-Channel in case in RC beam compare to other cases.

5. Conclusion

It is seen that,

- Load carrying capacity of section increases in case of double I section but it is similar to single I section with only 1% increase.
- In case of Center Position of GFRP composite beam deflection is minimum.
- GFRP C-channel section having minimum deflection than I-section GFRP beam.
- With less are I-section GFRP beam carries more load as compare to C-channel section GFRP beam.
- There is no any requirement of special treatment like drilling holes, riveting or welding. It is easy for connection to columns due to presence of the inside steel bars.

REFERENCES

1. Muhammad N.S. Hadi , Jian Song Yuan, "Experimental investigation of composite beams reinforced with GFRP I-beam and steel bars" Construction and Building Materials 144 (2017) 462-474
2. Tara sen, H.N. Jagannath reddy, "Flexural strengthening of RC beams using natural sisal and artificialcarbon and glass fabric reinforced composite system" Sustainable Cities and Society

- G Model SCS 128 1–13
3. Shilang Xu, Lijun Hou, Xiufang Zhang, “Flexural and shear behaviors of reinforced ultrahigh toughness cementitious composite beams without web reinforcement under concentrated load” *Engineering Structures* 39 (2012) 176–186
 4. Tara sen, H.N. Jagannath reddy, “Strengthening of RC beams in flexure using natural jute fiber textile reinforced composite system and its comparative study with CFRP and GFRP strengthening systems” *national Journal of Sustainable Built Environment* (2013) 2, 41–55
 5. S.T. Smith, J.G. Teng, FRP-strengthened RC beams. II: Assessment of debonding strength models, *Eng. Struct.* 24 (4) (2002) 397–417.
 6. J.F. Chen, J.G. Teng, Shear capacity of FRP-strengthened RC beams: FRP debonding, *Constr. Build. Mater.* 17 (1) (2003) 27–41.
 7. J.G. Teng, Y.M. Hu, Behaviour of FRP-jacketed circular steel tubes and cylindrical shells under axial compression, *Constr. Build. Mater.* 21 (4) (2007) 827–838.
 8. R.A. Walker, V.M. Karbhari, Durability based design of FRP jackets for seismic retrofit, *Compos. Struct.* 80 (4) (2007) 553–568.
 9. M.N.S. Hadi, W. Wang, M.N. Sheikh, Axial compressive behaviour of GFRP tube reinforced concrete columns, *Constr. Build. Mater.* 81 (2015) 198–207.
 10. W. Wang, M.N. Sheikh, M.N.S. Hadi, Behaviour of perforated GFRP tubes under axial compression, *Thin Walled Struct.* 95 (2015) 88–100.
 11. M.K. Sharbatdar, M. Saatcioglu, B. Benmokrane, Seismic flexural behavior of concrete connections reinforced with CFRP bars and grids, *Compos. Struct.* 93 (10) (2011) 2439–2449.
 12. C. Miàs, L. Torres, M. Guadagnini, A. Turon, Short and long-term cracking behaviour of GFRP reinforced concrete beams, *Composites Part B* 77 (2015) 223–231.
 13. T. Keller, Recent all-composite and hybrid fibre-reinforced polymer bridges and buildings, *Prog. Struct. Mater. Eng.* 3 (2) (2001) 132–140.
 14. A.M. Girão Coelho, J.T. Mottram, K.A. Harries, Bolted connections of pultruded GFRP: implications of geometric characteristics on net section failure, *Compos. Struct.* 131 (2015) 878–884.
 15. IS 10262 – 2009 Recommended guidelines for concrete mix design.
 16. IS 456 – 2000 code of practice for plain & reinforced cement concrete.
 17. IS 383 – 1970 Specification for coarse & fine aggregates from natural sources for concrete.