

The Characteristics of Electrodeposited Nickel composite coatings- A Review

Varadaraj S¹, Shreeprakash B¹, B.M. Praveen², Bharath K. Devendra^{2,3}

¹ Department of Mechanical Engineering, Srinivas University, Institute of Engineering & Technology, Mukka, Mangaluru, Karnataka, 574146, India.

² Department of Chemistry, Srinivas University, Institute of Engineering & Technology, Mukka, Mangaluru, Karnataka, 574146, India.

³ Department of Chemistry, M. S. Ramaiah College of Arts, Science and Commerce, MSR Nagar, MSRT Post, Bengaluru, Karnataka, 560054, India.

Abstract - For a long time, environmental protection of metallic components has become a pressing concern for the engineering and manufacturing industries. Coating technology has gained prominence to meet the needs of industrial demands. The coating is used to protect the metals and ensure the product's performance for a long time. Among other coating processes such as thermal spray, spark plasma sintering, and chemical vapour deposition, the electrodeposition process has proven to be the most cost-effective and simple. The paper discusses the properties of various Nickel composite electrodeposited Protective coatings.

Keywords: Protective Coatings, Electrodeposition, Nickel composites.

1. INTRODUCTION

Electrodeposition is one of the most successful method for coating metal due to its uncomplicated and consistent process which has unique advantages in the microstructure and property modification of the depositions. The components, phases, and microstructures of the deposits can be regulated by modifying the electrodeposition parameters, such as the deposition potential, current density, electrolyte composition, PH value, temperature, etc [1]. Due to flaws like wear, corrosion, and fatigue, a lot of machine parts fail. The characteristics like tribological, mechanical, and corrosion resistance are boosted by coating the reinforcing material on it [2]. The recommended method is nickel plating because it is renowned for its consistent plating thickness on the plated surface and the easiness with which intricate components can be coated. It also possesses exceptional levels of hardness and corrosion resistance [3]. The anti-wear qualities of the nickel coating have expanded their range of possible uses for dies, tools, and working parts for cars and other vehicles. With the available one, the spectrum of alloys might be expanded for functional purposes. By modifying the composite coating on the materials, it is feasible to avoid using pricey heat treatment procedures on standard alloys. [4]. The electro-chemical process is important in the field of nanotechnology. The co-deposition of composite material particles dispersion and the presence of these particles in the coating are accomplished using electrolyte baths containing micron/sub-micron-sized particles. The type of composite coating material particles and their inclusion determine the qualities of the coating material. [5][6].

2. Electrodeposition

Electrodeposition process can accomplish the reduction of the desired metal's cations before they are deposited on the surface of a conducting substrate. Two conductive electrodes are used in the coating setup, and they are submerged in an electrolyte bath. The working-cathode or electrode is thought to be a single terminal connected to the negative terminal. One more is referred to as a counter-electrode or anode and is attached to the positive terminal. The cations travel to the cathode, are discharged, and then deposit as a metallic layer when an external electric field is introduced. Electrodeposition is the ideal technique for achieving a smooth and ideal contact between the matrix metal and ceramic particles. [7][8]. Electrodeposition, often known as electroplating, is a technique for electrolytically depositing a coating on a substrate that is immersed in an electrolyte. An aqueous medium at room temperature can be used for this. Aqueous solution electroplating refers to the method of electroplating aqueous solutions at room temperature. using a fused-salt solution, also known as electroplating, or in a high-temperature fusion salt. One of the major drawbacks of electrodeposition is the inability to obtain consistency in coating thickness. Other limitations of the substrate include hydrogen ion assessment and essential surface preparation [9]. Electrodeposition is widely utilised for aesthetic coatings as well as corrosion and wear resistance. It is also used in specialised applications including high temperature resistance, biomedical, and ceramic coating by increasing the electrode potential [10]. Electrodeposition can produce metallic systems with all of these dimensionalities, while three-dimensional systems have the largest variety of applications [11]. Both direct (DC) and pulse current can be used in the electrodeposition process (PC). The

coating can be applied to the substrate's surface to improve solderability, lubricating characteristics, electrical conductivity, corrosion resistance, wear and thermal resistance[12]. Deep recesses and irregularly shaped geometries can be deposited upon using electrodeposition with less sophisticated plating conditions and equipment [13].

3. Composite Coating

Composite coating is a new type of coating developed by modern experts. Normally, several types of composite materials are used depending on the matrix. Examples of these materials composites include ceramic matrix composites and metal matrix composites. Composites include things like carbon matrix composites and polymer matrix composites [14]. Metal matrix composite coating is one of the most widely utilised in the industry due to its efficiency [15]. MMC coatings, which combine the ceramic phase's high hardness and strength with the matrix's sound toughness, are frequently utilised for surface repair and strengthening of engineering metal components. The inclusion of reinforcing particles can be done in two ways. Due to the low wetting capabilities of the ceramic and metallic phases, particle-matrix bonding is fundamentally difficult with external addition or ex situ. The ceramic reinforcing phase of the coating is created by an in-situ chemical reaction between elements of the precursor material at a very high temperature, followed by in situ nucleation and growth. These hard particles are consequently more thermodynamically stable and finer than hard particles injected from the outside. There are multiple sorts and designs of composite coatings. Composite coatings of different forms, shapes, sizes, and quality can be produced by choosing the right ceramic and matrix coating materials, procedures, and technologies [16]. Al, Fe, Mg, Ti, Ni, Be and Co are some of the commonly used materials for metal matrix composites [17,18]. Metal matrix composites' (MMC) properties are generally determined by their composition and structure [19]. To maximize coating characteristics, a homogeneous distribution and large number of particles participating in the metal matrix are required [20,21]. Enhanced coating performance is often caused by modifications to the growth mode or grain size of the metal matrix. [21,22]. The size, diversity, and shape of the implanted particles, as well as current density, pH, electrolyte agitation, and bath composition, are all dependent factors that affect particle incorporation [23]. Due to the enormous potential for developing materials with specialised features, MMCs have found use in a variety of fields [13]. The Ni-based MMC coating is one of the most challenging and interesting metal matrix coatings [15]. Many composite coatings have been extensively electrodeposited, including Ni-SiC, Al₂O₃, TiO₂, ZrO₂, Si₃N₄, Mo, Cr, and others [8]. Nickel-based composite coatings have opened up new possibilities because of their exceptional wear and corrosion resistance as well as their high hardness[15]. On tribological parameters including coefficient of friction, hardness, roughness, and wear rate, various alloying elements and hard particles incorporated in the nickel matrix have a variety of effects. These factors can cause the value of characteristics to rise or fall [24]

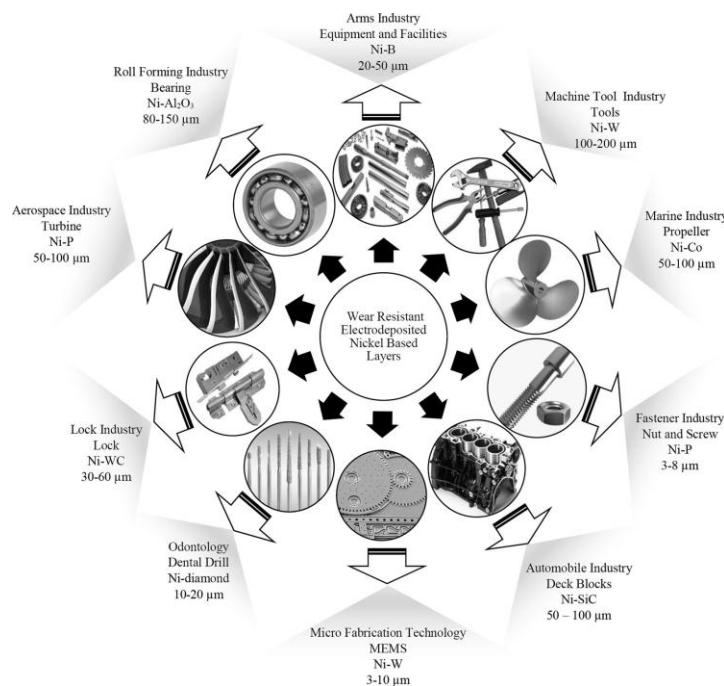


Fig -1: Applications of Electrodeposited Nickel coating [24]

Numerous chemical, mechanical, and electrical processes require nickel and alloys including nickel phosphorous, nickel tungsten, nickel cobalt, and others. The importance of composite coatings with superior wear resistance is rising along with the demand for longer industrial component service lives [25]. The applications of nickel composite coatings are shown in Fig. 1, which range from the maritime sector to the lock industry. The addition of the particles raises the coating's hardness and wear resistance while also lowering its coefficient of friction. Among other engineering components, a nickel-based coating is applied to cutting tools, turbine blades, rollers, plungers, rolling mill rolls, extruders, piston heads, and rods [15].

3.1 Similar Electrodeposition work carried out

Mohan reddy et al. [26] studied the electrodeposition procedure used to make a Ni-Si₃N₄ coating. More corrosion resistance was seen in Ni-Si₃N₄ nanocomposites containing 3 g/L Si₃N₄ nanoparticles in the bath solution. The performance of Ni-Si₃N₄ nanocomposites prepared in the presence of SDS was subpar in comparison to Ni-Si₃N₄ nanocomposites prepared without SDS. Without the use of a surfactant, Ni-Si₃N₄ nanocomposites have higher corrosion resistance and particle inclusion. In the investigation, about 9% of the nanoparticles were deposited in the coating.

D Rashmi et al. [27] investigated the electrofabrication of nanostructured Ni-Fe alloy coatings on mild steel using a sulphate bath. For the coating, the composition of the electrolytic bath and current density were adjusted. Energy dispersive X-ray spectroscopy has been used to identify the composition of the Ni-Fe alloy. The coatings are unique in kind. Tests for corrosion using potentiodynamic polarisation and electrochemical impedance Spectroscopic techniques indicate that 4 A dm⁻² is the lowest corrosion rate in a solution of 3.5 percent NaCl. The Vickers hardness test and atomic force microscopy were used to measure the coatings' hardness and roughness, respectively. The surface morphology of the coatings was examined using scanning electron microscopy. X-ray diffraction was used to calculate and analyse the texture coefficient, phase structure, and crystallite grain size of the coating.

Roberta Lee et al. [28] investigated the electrodeposition of niobium oxide from a variety of aqueous and non-aqueous solvent systems using sol-gel processing techniques. The process depends on protons and hydroxide ions being produced electrochemically by adjusting the electrochemical pH of the solution. In non-aqueous solutions containing tertiary niobium alkoxides, two-electron reduction results in hydroxide ions. In aqueous alkaline systems containing niobate, water undergoes electrochemical oxidation, which results in a pH drop. Niobium oxide and mixed niobate are created as the niobate sol destabilises and an electrode coating forms.

Bapu Gr et al. [29] studied the dispersion-strengthened nickel was generated utilising the electro-codeposition method using a nickel fluoroborate electrolyte containing vanadium pentoxide (V₂O₅) particles in solution. The effects of particle size, particle concentration in the bath, current density, pH, and temperature on the volume percent (vol. percent) integration of V₂O₅ particles in the composite were investigated. Investigation and comparison of the composite's corrosion behaviour in a 5% sodium chloride (NaCl) solution with mild steel and nickel deposits were also conducted. The percentage of V₂O₅ particles in the composite increased with rising V₂O₅ content in the bath and rising current density. The bath's operation at 6.0 amp dm⁻², pH 3.0, and 50 °C produced the best incorporation of V₂O₅ (12.6 vol. percent). According to corrosion testing, the composite prevents steel from corroding when there is NaCl present. In a NaCl solution with a pH of 3.0, the composites' corrosion resistance is weaker to that of nickel deposits, but in a NaCl solution with a pH of 6.5, they offer comparable defence.

3.2 Components of Electrolytic bath

The preparation of the electrolytic bath with the right proportion is very much essential for the electrodeposition quality. The nickel electrodeposition mainly consists of Nickel sulphate, Nickel Chloride and Boric acid in its electrolytic solution. The related particles zinc, graphene, iron etc are to be added with required proportion for nickel composite coating along with the electrolytic solution. The electrolytic composition data of the various composite coatings are given in the table.

SDS (Sodium Do-Decyl Sulphate), an anionic surfactant, has been shown to boost the coating's hardness and improve its adherence to the matrix [30]. The corrosion resistance has increased and the particle distribution has become more uniform due to the addition of more SDS, a surfactant, to the electrolytic solution for Ni-Alumina [31]. The composition and operational parameters of various Nickel composite coatings are listed in Table 1.

Table1- Composition and parameters of electrolytic bath

Composite Coating	NiSo ₄ .6H ₂ O (Nickel Sulphate) (gL ⁻¹)	NiCl ₂ .6H ₂ O (Nickel Chloride)(gL ⁻¹)	H ₃ B0 ₃ (gL ⁻¹)	Particles (gL ⁻¹)	pH	Temperature (°C)	Current Density (A dm ⁻²)	Time (min)	Reference
Nickel-graphene	85-100	12 to 15	25-35	0.2	3 - 4	45±5°C	5	60	[32]
Nickel-Graphene	330	35	40	0.1	3.5	51±1°C	5	55	[33]
Nickel-Graphene	300	50	40	0.5,0.25,0.1	4±2	45±5°C	5	50-60	[34]
Nickel-Graphene	26.26	56.81	18.54	0.1	3.8-4	40°C	5.66	50	[35]
Nickel-Graphene	110-115	18-25	35-45	0.2,0.4	3 - 4	50°C	5	30	[36]
Nickel-Graphene oxide	240	45	30	0.1(GO)	3.5 - 4.5	55-60 °C	6 to 10	65	[37]
Nickel-Reduced Graphene oxide	250	35	35	4.37	3 - 4	55°C	3.5	12 h	[38]
Nickel-Graphene	300	35	40	0.05	4±1	50°C	0.15-4	1-3 hours	[39]
Nickel-Graphene	95-110	15-20	30-40	0.2	3-4	50-55 °C	5	50	[40]
Nickel-Vanadium pentoxide	280	5	40	5 to 50	1- 5	30-70 °C	2 to 10	8h	[29]
Nickel-Si ₃ N ₄	27	57	19	3	3	40°C	5	60	[41]

As per the various literature data being listed out in the Table 1 it is understood that high temperature is the prerequisite for electrodepositing nickel composite coating. Temperature ranging from 50-60°C is required for nickel composite electrodeposition. The PH is to be maintained between 3-4 and an average current density of 5-6 A/dm² is to be maintained during the process. Most of the researchers have carried out the electrodeposition work for 60 mins.

4. Results and discussions

The commonly measured result parameters of the electrodeposited coatings are surface morphology, Corrosion potential, Roughness, Microhardness and Contact angle measurements. The various results of Nickel composites are listed in Table 2.

Table 2- Results Summary of Nickel composites

Coating Composition	XRD /EDAX Analysis	Corrosion Potential	Microhardness	SEM Analysis	AFM Analysis	Ref
Ni-Si ₃ N ₄	Peaks detected for Ni, Si ₃ N ₄ not detected due to lower concentration	Improved corrosion resistance observed with current of 0.00812 A/cm ² .	Increased hardness value observed with about 400HV	More uniform grain structure is observed	Hill- valley like structure with homogenous distribution of grains	[26]

Ni- Fe alloy	Increased percentage of Ni was observed than Fe	Coating at $4a/dm^{-2}$ demonstrated maximum corrosion resistance.	Increasing Trend observed till coatings of current density $4a/dm^{-2}$	Homogenity and grain size increased with the current density.	The roughness value increased with the increase in current density.	[27]
Ni- Nb	The bath containing the Maximum Nb content (50 μm) led to least deposition of niobium.	Improved corrosion resistance was observed	The microhardness of the Ni-Nb coating improved	Good particle distribution was obtained for 20 μm particles.	NA	[42]
Ni-Gr	Higher carbon content attained with the increase in surfactant (SDS)	Enhanced corrosion resistance observed as the surfactant (SDS) increases.	The microhardness increased with the increase in SDS content.	Bulge morphology is observed in 0.4 g/l SDS content coating.	The roughness has greatly enhanced with the use of anionic surfactant..	[32]
Ni-Gr	Reduction in Crystallite size is observed with growing nucleate size.	Ni-Gr composite coating has high corrosion resistance.	Compared to the Ni coating, the Ni-Gr composite coating demonstrated greater hardness.	Fine grained structure with intact arrangement of Ni ions is observed	NA	[43]
Ni-Zn	γ Phase is observed from the different intensities.	Improved corrosion resistance observed for both alkaline and acidic deposition.	The hardness value was found to be 97 ± 4 HV	Pyramid Structure with porosity levels observed in the coating.	The coatings obtained at lower current densities had more uniform grain distribution.	[44], [45]
Ni-TiO ₂	Both the nickel and TiO ₂ peaks were observed.	The corrosion resistance increased with the TiO ₂ Content.	Increase in TiO ₂ and surfactant showed an increasing trend in Microhardness.	Nickel facets along TiO ₂ particles with sizes less than 2 m.	Roughness value increased with the addition of TiO ₂ particles	[46], [47]
Ni-MoS ₂	Sharp peaks observed for the composition.	Better corrosion resistance observed for the composite coating.	The composite coating is harder than mild steel specimen.	Crystallinity structure was clearly visible.	NA	[48]
Ni- Co ₃ O ₄	Related peaks of the composition were found	Corrosion resistance improved for the composite coating	The hardness number increased for the composite coating.	Pyramid type protuberance was observed	NA	[49]
Ni-B-Al ₂ O ₃	Mainly Single broad peaks observed,The presence of all the elements confirmed	Improvement in corrosion behaviour is observed for addition of both the elements	Increased microhardness observed for the composite coating	Uniform , well crystallized dense structure is observed	Rough surfaces are revealed in the composite coating	[50]
Ni-B-V ₂ O ₅	Single clear peak is being reflected in the XRD pattern.	Improved corrosion resistance observed with the addition of V ₂ O ₅	The microhardness increased for the addition of V ₂ O ₅	Homogenous distribution of the Particles observed with few microcracks	Surface roughness increased with the addition of V ₂ O ₅	[51]

Ni-Co-CeO ₂	Addition of CeO ₂ influenced the growth of the crystallites	Corrosion resistance increased with the addition of CeO ₂	With the addition of CeO ₂ , the composite coating's microhardness enhanced..	Polyhedral crystals to nodular crystals have been observed	NA	[52]
------------------------	--	--	--	--	----	------

The results of the various nickel composite electrodeposition coatings have been presented in table 2. It was found from the literatures that mild steel was the most commonly used substrate and it is widely used material in industries, and hence it is prone to corrosion. The mechanical properties, surface characteristics and corrosion potentials have been listed for most of the varieties of nickel composite coating. Researchers have discovered the better surface properties and corrosion resistance which could pave the path for widespread usage in the industrial and commercial usage.

4.1 Corrosion Investigation Techniques:

Tafel extrapolation method and AC impedance method are the most commonly used corrosion resistance measurements methods. Tafel extrapolation method uses potential excitation in the form of direct current to give larger and appreciable currents to measure the corrosion rate, Since the current and potential are non linear, semi logarithmic plots is obtained called as Tafel Plots. Utilizing alternating current potential excitation, the AC impedance measuring approach offers crucial details on the capacitive behaviour of the double layer that contributes to the coatings' corrosion resistance. It offers details on the polarity and quantity of charges present at the electrode and electrolyte, which are easily comprehended by examining the impedance curves.

5. Research Gap

All of the studies described that inclusion of particles like Graphene, Niobium, Vanadium, Titanium Oxide, Zinc and boron with nickel by electrodeposition has proved to provide enhanced corrosion resistance and mechanical characteristics. The majority of the researchers have not focused on the lower electrolyte concentration of the particles, further the mechanical properties like microhardness, scratch resistance, roughness, profile and contact angle are barely unexplored.

6. Conclusion

Nickel is increasingly used in many new fields, putting it in competition with other materials due to its special combination of qualities and traits and its many industrial applications. This has led to the development of innovative nickel processing methods. The review paper provides a comprehensive overview of the overall elements of electrodeposition of nickel composite coating. Nickel Composite coating have been vastly researched with various combination of the particles. The inclusion of nanoparticles in the coating exhibit improved properties in terms of roughness, microhardness, and corrosion resistance with an uniform distribution of the particles. The electrodeposition of these particles at lower concentrations with nickel and its impact on corrosion and mechanical properties must be explored in the current study. The researchers can start working on the analysis with the help of this paper.

REFERENCES

- [1] Y.H. Ahmad, A.M.A. Mohamed, (2014). Electrodeposition of nanostructured nickel-ceramic composite coatings: a review, Int. J. Electrochem. Sc. 9 1942-1963.
- [2] Raghavendra CR, Basavarajappa S, SogaladI, (2016). Electrodeposition of Ni–Al₂O₃ nano composite coating and evaluation of wear characteristics. IOP Sci. <https://doi.org/10.1088/1757-899x/149/1/012110>
- [3] Smrithi, S. P., Kottam, N., & Vergis, B. R. (2022). Heteroatom modified hybrid carbon quantum dots derived from Cucurbita pepo for the visible light driven photocatalytic dye degradation. *Topics in Catalysis*, 1-12. <https://doi.org/10.1007/s11244-022-01581-x>
- [4] Casati, R., & Vedani, M. (2014). Metal matrix composites reinforced by nano-particles—a review. *Metals*, 4(1), 65-83. <https://doi.org/10.3390/met4010065>

- [5] Aruna, S. T., Bindu, C. N., Selvi, V. E., Grips, V. W., & Rajam, K. S. (2006). Synthesis and properties of electrodeposited Ni/ceria nanocomposite coatings. *Surface and Coatings Technology*, 200(24), 6871-6880. <https://doi.org/10.1016/j.surfcoat.2005.10.035>
- [6] Zhou, Y., Zhang, H., & Qian, B. (2007). Friction and wear properties of the co-deposited Ni-SiC nanocomposite coating. *Applied surface science*, 253(20), 8335-8339. <https://doi.org/10.1016/j.apsusc.2007.04.047>
- [7] Yang, Y., & Cheng, Y. F. (2013). Mechanistic aspects of electrodeposition of Ni-Co-SiC composite nano-coating on carbon steel. *Electrochimica Acta*, 109, 638-644. <https://doi.org/10.1016/j.surfcoat.2005.10.035>
- [8] Torabinejad, V., Rouhaghdam, A. S., Aliofkhaezai, M., & Allahyarzadeh, M. H. (2016). Electrodeposition of Ni-Fe and Ni-Fe-(nano Al₂O₃) multilayer coatings. *Journal of Alloys and Compounds*, 657, 526-536. <https://doi.org/10.1016/j.jallcom.2015.10.154>
- [9] Davis, J. R. (Ed.). (2001). *Surface engineering for corrosion and wear resistance*. ASM international. <https://doi.org/10.31399/asm.tb.secwr.9781627083157>
- [10] Fotovvati, B., Namdari, N., & Dehghanghadikolaie, A. (2019). On coating techniques for surface protection: A review. *Journal of Manufacturing and Materials processing*, 3(1), 28. <https://doi.org/10.3390/jmmp3010028>
- [11] Bicelli, L. P., Bozzini, B., Mele, C., & D'Urzo, L. (2008). A review of nanostructural aspects of metal electrodeposition. *Int. J. Electrochem. Sci*, 3(4), 356-408. <https://doi.org/10.1149/1.1869976>
- [12] Chandrasekar, M. S., & Pushpavanam, M. (2008). Pulse and pulse reverse plating—Conceptual, advantages and applications. *Electrochimica Acta*, 53(8), 3313-3322. <https://doi.org/10.1016/j.electacta.2007.11.054>
- [13] Chaudhari, A. K., & Singh, V. B. (2018). A review of fundamental aspects, characterization and applications of electrodeposited nanocrystalline iron group metals, Ni-Fe alloy and oxide ceramics reinforced nanocomposite coatings. *Journal of Alloys and Compounds*, 751, 194-214. <https://doi.org/10.1016/j.jallcom.2018.04.090>
- [14] Park, S. J., & Seo, M. K. (2011). *Interface science and composites* (Vol. 18). Academic Press. <https://doi.org/10.1016/b978-0-12-375049-5.00007-4>
- [15] Karmakar, R., Maji, P., & Ghosh, S. K. (2021). A review on the nickel based metal matrix composite coating. *Metals and Materials International*, 27(7), 2134-2145. <https://doi.org/10.1007/s12540-020-00872-w>
- [16] Reddy, R. M., Praveen, B. M., & Alhadhrami, A. (2021). Characterization & electrochemical behavior of DC & PC methods of electrodeposited Ni-TiO₂-CNTs nanocomposite coatings. *Physica Scripta*, 96(12), 125719. <https://doi.org/10.1088/1402-4896/ac33fa>
- [17] Smrithi, S. P., Kottam, N., Narula, A., Madhu, G. M., Mohammed, R., & Agilan, R. (2022). Carbon dots decorated cadmium sulphide heterojunction-nanospheres for the enhanced visible light driven photocatalytic dye degradation and hydrogen generation. *Journal of Colloid and Interface Science*, 627, 956-968. <https://doi.org/10.1016/j.jcis.2022.07.100>
- [18] Maji, P., Ghosh, S. K., Nath, R. K., & Karmakar, R. (2020). Microstructural, mechanical and wear characteristics of aluminum matrix composites fabricated by friction stir processing. *Journal of the Brazilian Society of Mechanical Sciences and Engineering*, 42(4), 1-24. <https://doi.org/10.1007/s40430-020-02279-5>
- [19] Rathod, M.R., Rajappa, S.K., Minagalavar, R.L., Praveen, B.M., Bharath, D. K., & A.A. Kittur. (2022). Investigation of African mangosteen leaves extract as an environment-friendly inhibitor for low carbon steel in 0.5M H₂SO₄. *Inorganic Chemistry Communications*, 109488. <https://doi.org/10.1016/j.inoche.2022.109488>.
- [20] Garcia, I., & Conde, A. (2003). G. langelaan, J. fransaer, JP Celis, Improved corrosion resistance through microstructural modifications induced by codepositing SiC-particles with electrolytic nickel. *CorrosSci*, 45, 1173-1189. [https://doi.org/10.1016/s0010-938x\(02\)00220-2](https://doi.org/10.1016/s0010-938x(02)00220-2)
- [21] Bund, A., & Thiemig, D. (2007). Influence of bath composition and pH on the electrocodeposition of alumina nanoparticles and nickel. *Surface and Coatings Technology*, 201(16-17), 7092-7099. <https://doi.org/10.1016/j.surfcoat.2007.01.010>

- [22] Zimmerman, A. F., Clark, D. G., Aust, K. T., & Erb, U. (2002). Pulse electrodeposition of Ni–SiC nanocomposite. *Materials letters*, 52(1-2), 85-90. [https://doi.org/10.1016/s0167-577x\(01\)00371-8](https://doi.org/10.1016/s0167-577x(01)00371-8).
- [23] Thiemig, D., Lange, R., & Bund, A. (2007). Influence of pulse plating parameters on the electrocodeposition of matrix metal nanocomposites. *Electrochimica Acta*, 52(25), 7362-7371. <https://doi.org/10.1016/j.electacta.2007.06.009>
- [24] Mahidashti, Z., Aliofkhaezai, M., & Lotfi, N. (2018). Review of nickel-based electrodeposited tribo-coatings. *Transactions of the Indian Institute of Metals*, 71(2), 257-295. <https://doi.org/10.1007/s12666-017-1175-x>
- [25] Lekka, M., Bonora, P. L., Lanzutti, A., Benoni, S., Caoduro, P., & Fedrizzi, L. (2012). Industrialization of Ni- SiC electrodeposition on copper moulds for steel continuous casting. *La Metallurgia Italiana*. <https://doi.org/10.1016/j.surfcoat.2012.03.016>
- [26] Mohan Reddy, R., Praveen, B. M., Kumar, P., & Venkatesha, T. V. (2017). Ni–Si₃N₄: Electrodeposition, properties and corrosion behavior. *Surface Engineering and Applied Electrochemistry*, 53(3), 258-264. <https://doi.org/10.3103/s1068375517030127>
- [27] Rashmi, D., Pavithra, G. P., Praveen, B. M., & Devapal, D. (2020). Development of Nanostructured Ni–Fe Alloy Coatings; Characterisation and Corrosion Analysis. *Surface Engineering and Applied Electrochemistry*, 56(1), 46-54. <https://doi.org/10.3103/s1068375520010135>
- [28] RobertáLee, G. (1996). Studies on the electrochemical deposition of niobium oxide. *Journal of Materials Chemistry*, 6(2), 187-192. <https://doi.org/10.1039/jm9960600187>
- [29] Bapu, G. R., & Yusuf, M. M. (1993). Electrodeposition of nickel-vanadium pentoxide composite and its corrosion behaviour. *Materials Chemistry and Physics*, 36(1-2), 134-138. [https://doi.org/10.1016/0254-0584\(93\)90020-m](https://doi.org/10.1016/0254-0584(93)90020-m)
- [30] Devendra, B. K., Praveen, B. M., Tripathi, V. S., Nagaraju, G., Nagaraju, D. H., & Nayana, K. O. (2021). Highly Corrosion Resistant Platinum-Rhodium alloy coating and its photocatalytic activity. *Inorganic Chemistry Communications*, 134, 109065. <https://doi.org/10.1016/j.inoche.2021.109065>.
- [31] Sabri, M., Sarabi, A. A., & Kondelo, S. M. N. (2012). The effect of sodium dodecyl sulfate surfactant on the electrodeposition of Ni-alumina composite coatings. *Materials Chemistry and Physics*, 136(2-3), 566-569. <https://doi.org/10.1016/j.matchemphys.2012.07.027>
- [32] Yasin, G., Arif, M., Nizam, M. N., Shakeel, M., Khan, M. A., Khan, W. Q., & Zuo, Y. (2018). Effect of surfactant concentration in electrolyte on the fabrication and properties of nickel-graphene nanocomposite coating synthesized by electrochemical co-deposition. *RSC advances*, 8(36), 20039-20047. <https://doi.org/10.1039/c7ra13651j>
- [33] Devendra, B. K., Praveen, B. M., Tripathi, V. S., Kumar, H. P., & Chethana, K. R. (2022). The development of platinum-rhodium alloy coatings on SS304 using a pulse/direct electrodeposition technique and their application to antibacterial activity. *Journal of the Indian Chemical Society*, 99(6), 100466. <https://doi.org/10.1016/j.jics.2022.100466>
- [34] Algul, H., Tokur, M., Ozcan, S., Uysal, M., Çetinkaya, T., Akbulut, H., & Alp, A. (2015). The effect of graphene content and sliding speed on the wear mechanism of nickel–graphene nanocomposites. *Applied Surface Science*, 359, 340-348. <https://doi.org/10.1016/j.apsusc.2015.10.139>
- [35] Siddaiah, A., Kumar, P., Henderson, A., Misra, M., & Menezes, P. L. (2019). Surface energy and tribology of electrodeposited Ni and Ni–graphene coatings on steel. *Lubricants*, 7(10), 87. <https://doi.org/10.3390/lubricants7100087>
- [36] Yasin, G., Khan, M. A., Arif, M., Shakeel, M., Hassan, T. M., Khan, W. Q., ... & Zuo, Y. (2018). Synthesis of spheres-like Ni/graphene nanocomposite as an efficient anti-corrosive coating; effect of graphene content on its morphology and mechanical properties. *Journal of Alloys and Compounds*, 755, 79-88. <https://doi.org/10.1016/j.jallcom.2018.04.321>
- [37] Singh, S., Samanta, S., Das, A. K., & Sahoo, R. R. (2018). Tribological investigation of Ni-graphene oxide composite coating produced by pulsed electrodeposition. *Surfaces and Interfaces*, 12, 61-70. <https://doi.org/10.1016/j.surfin.2018.05.001>

- [38] Devendra, B.K., & Praveen B.M. (2019). A Review on Noble Metals in Controlling Intergranular Stress Corrosion Cracking in BWRs. *International Journal of Applied Engineering and Management Letters (IJAEML)*, 3 (1): 53-59. <https://zenodo.org/record/2653464>.
- [39] Ren, Z., Meng, N., Shehzad, K., Xu, Y., Qu, S., Yu, B., & Luo, J. K. (2015). Mechanical properties of nickel-graphene composites synthesized by electrochemical deposition. *Nanotechnology*, 26(6), 065706. <https://doi.org/10.1088/0957-4484/26/6/065706>
- [40] Jabbar, A., Yasin, G., Khan, W. Q., Anwar, M. Y., Korai, R. M., Nizam, M. N., & Muhyodin, G. (2018). Electrochemical deposition of nickel graphene composite coatings: effect of deposition temperature on its surface morphology and corrosion resistance, *RSC Adv.* 7 (2017) 31100–31109. <https://doi.org/10.1039/c6ra28755g>
- [41] Reddy, R. M., Praveen, B. M., Chandrappa, K. G., & Nayana, K. O. (2016). Generation of Ni–Si₃N₄ nanocomposites by DC, PC and PRC electrodeposition methods. *Surface Engineering*, 32(7), 501-507. <https://doi.org/10.1080/02670844.2016.1148323>
- [42] Fratari, R. Q., & Robin, A. (2006). Production and characterization of electrolytic nickel–niobium composite coatings. *Surface and Coatings Technology*, 200(12-13), 4082-4090. <https://doi.org/10.1016/j.surfcoat.2005.02.168>
- [43] Kumar, C. P., Venkatesha, T. V., & Shabadi, R. (2013). Preparation and corrosion behavior of Ni and Ni–graphene composite coatings. *Materials Research Bulletin*, 48(4), 1477-1483. <https://doi.org/10.1016/j.materresbull.2012.12.064>
- [44] Gavrilă, M., Millet, J. P., Mazille, H., Marchandise, D., & Cuntz, J. M. (2000). Corrosion behaviour of zinc–nickel coatings, electrodeposited on steel. *Surface and coatings technology*, 123(2-3), 164-172. [https://doi.org/10.1016/S0257-8972\(99\)00455-7](https://doi.org/10.1016/S0257-8972(99)00455-7)
- [45] Kumar, C. M. P., Lakshmikanthan, A., Chandrashekarappa, M. P. G., Pimenov, D. Y., & Giasin, K. (2021). Electrodeposition based preparation of Zn–Ni alloy and Zn–Ni–WC nano-composite coatings for corrosion-resistant applications. *Coatings*, 11(6), 712. <https://doi.org/10.3390/coatings11060712>
- [46] Parida, G., Chaira, D., Chopkar, M., & Basu, A. (2011). Synthesis and characterization of Ni–TiO₂ composite coatings by electro-co-deposition. *Surface and Coatings Technology*, 205(21-22), 4871-4879. <https://doi.org/10.1016/j.surfcoat.2011.04.102>
- [47] Chen, W., & Gao, W. (2010). Sol-enhanced electroplating of nanostructured Ni–TiO₂ composite coatings—the effects of sol concentration on the mechanical and corrosion properties. *Electrochimica Acta*, 55(22), 6865-6871. <https://doi.org/10.1016/j.electacta.2010.05.079>
- [48] Gana, A., Ben Temam, H., Lekmine, F., Naoun, M., & Herzallah, O. (2021). Characterization of electrodeposited Ni–MoS₂ composite coatings under the influence of current density. *Digest Journal of Nanomaterials & Biostructures (DJNB)*, 16(3). <https://doi.org/10.15251/djnb>
- [49] Akhtar, K., Khalid, H., UlHaq, I., Zubair, N., Ullah Khan, Z., & Hussain, A. (2017). Tribological properties of electrodeposited Ni–Co₃₀₄ nanocomposite coating on steel substrate. *Journal of Tribology*, 139(6). <https://doi.org/10.1115/1.4036450>
- [50] Shakoor, R. A., Kahraman, R., Waware, U., Wang, Y., & Gao, W. (2014). Properties of electrodeposited Ni–B–Al₂O₃ composite coatings. *Materials & Design*, 64, 127-135. <https://doi.org/10.1016/j.matdes.2014.07.026>
- [51] Manohar Rathod, Rajappa, S.K., Praveen, B.M., & Bharath, D.K. (2021). Investigation of Dolichandra unguis-cati leaves extract as a corrosion inhibitor for mild steel in acid medium. *Current Research in Green. And Sustainable Chemistry*. 4, 100113. <https://doi.org/10.1016/j.crgsc.2021.100113>.
- [52] Srivastava, M., Grips, V. W., & Rajam, K. S. (2010). Electrodeposition of Ni–Co composites containing nano-CeO₂ and their structure, properties. *Applied Surface Science*, 257(3), 717-722. <https://doi.org/10.1016/j.apsusc.2010.07.046>